

In-vitro evaluation of bond strength of four self-etching cements

Julio Chávez-Lozada, Carmen Urquía-Morales

Universidad Nacional de Córdoba, Facultad de Odontología,
Cátedra de Operatoria I, Córdoba, Argentina

ABSTRACT

Indirect restorations need to be attached with adhesive luting agents to prevent them from becoming dislodged and provide adequate marginal sealing. The aim of this study was to evaluate bond strength to dentin of self-etching resin cements. Materials and methods: 75 flat dentin surfaces were randomly distributed among 5 groups, according to cements used; Group 1: RelyxU100 (3M/ESPE), Group 2: Bis Cem (Bisco), Group 3: Max Cem (Kerr), Group 4: SeT PP (SDI) and Group 5: Relyx ARC (3M/ESPE), control. Ceramic test cylinders (IPS Empress 2 / Ivoclar-Vivadent) 4.1 mm across were prepared and attached to the dentin surfaces using the different cements. A constant 25N load was applied for 1 minute and they were light-polymerized. Following storage for 24 hours at 100% humidity and 37 °C, the specimens were tested for bond strength under shear strain in an

Instron testing machine at a crosshead speed of 1 mm/minute; at 7, 14 and 21 days. Data were analyzed by ANOVA and Tukey's test. There were significant differences between materials ($p < 0.0001$), but not between times or material/time interaction. RelyX ARC (Control Group) had the highest bond strength (15.52 MPa). Among the self-etching cements, the best behavior was found for Relyx U100 (10.80MPa), followed by BisCem (6.36 MPa), MaxCem (5.45 MPa) and SeTPP (3.17 MPa). The bond strength of the self-adhesive cements evaluated was lower than that for resin cements which require previous treatment of the dental substrate (control group). This should be taken into account during clinical selection, in particular for tooth preparations with poor retention.

Key words: Dental cements. Resin cements. Dental bonding.

Evaluación in vitro de la resistencia adhesiva de cuatro cementos de autograbado

RESUMEN

Las restauraciones indirectas deben ser fijadas por medio de agentes cementantes, para evitar su desprendimiento y mantener un adecuado sellado marginal. El objetivo de este trabajo fue evaluar la resistencia adhesiva a dentina de los cementos resinosos de autograbado. Materiales y métodos: Se utilizaron 75 superficies planas de dentina, distribuidos aleatoriamente en 5 grupos, según los medios cementantes; GRUPO 1: RelyxU100 (3M/ESPE), GRUPO 2: Bis Cem (Bisco), GRUPO 3: Max Cem (Kerr), GRUPO 4: SeT PP (SDI) y GRUPO 5: Relyx ARC (3M/ESPE), control. Se confeccionaron probetas cilíndricas de cerámica (IPS Empress 2 / Ivoclar-Vivadent) de 4,1 mm de diámetro, las que fueron fijadas a las superficies de dentina mediante los distintos cementos. Se aplicó una carga constante de 25N durante 1 minuto y se realizó la fotopolimerización. Después de 24 horas de almacenamiento en un medio con 100 % de humedad a 37° C, las probetas fueron sometidas a ensayo de

resistencia adhesiva bajo tensiones de corte en máquina Instron, con una velocidad del cabezal de 1 mm/minuto; a los 7, 14 y 21 días. Los datos fueron analizados mediante ANOVA y test de Tukey, mostrando diferencias significativas entre los materiales ($p < 0,0001$), no así respecto al factor tiempo ni a su interacción. El mayor valor de resistencia adhesiva lo presentó RelyX ARC (Grupo control) (15,52MPa), De los cementos autograbantes, el mejor comportamiento se obtuvo en Relyx U100 (10,80MPa), seguido por BisCem (6,36MPa), MaxCem (5,45MPa) y SeTPP (3,17MPa): Los cementos autoadhesivos evaluados presentaron menor resistencia adhesiva que los cementos resinosos que requieren tratamiento previo del sustrato dentario (grupo control). Esto debería ser considerado cuando se realiza su selección clínica, sobre todo en preparaciones dentarias poco retentivas.

Palabras clave: cementos dentales, cementos resinosos, adhesivo dental.

INTRODUCTION

When teeth lose their structural, functional and/or aesthetic integrity, they may be restored by inserting plastic or rigid materials. When much of the dental structure is lost, the use of plastic materials has well-known limitations, and partial or total rigid crown restorations (metal or aesthetic) are indicated. Rigid restorations must be bonded to the dental structures by luting agents to prevent them

from becoming detached and provide adequate marginal sealing, ensuring their permanence in the oral cavity¹.

Despite the advantages of rigid restorations (resistance to abrasion, resistance to fractures, polymerization control, adequate contour anatomy and contact relationship²), bonding them to the tooth structure is still a challenge because this type of restoration doubles the adhesive interfaces: one

interface at the tooth surface and the other at the surface of the restoration.

Society's aesthetic demand has motivated dental product manufacturers to develop metal-free restorative materials such as porcelain or compound resin onlays, veneers and crowns³. The possibility of restoring to each tooth not only form and function but also visual harmony between the restoration and the remaining tooth, in addition to the characteristics of its integration, make aesthetic onlays a valid alternative to plastic or cast metal restorations when there is significant destruction of tooth tissues, exceeding one third of intercuspal distance⁴. The preparations made for these restorations are more conservative, and regarding the bonding materials, the basic aim is to increase bond strength to the different substrates, i.e. it involves not only selecting a material with good bonding properties, but also proper preparation of the substrates to be bonded⁵.

Bonding rigid restorations requires different mechanisms to ensure retention, such as the creation of opposing surfaces that can make close contact in order to achieve friction. This contact needs to be improved by interposing a liquid which in turn can be hardened by means of a chemical or physical mechanism – the luting agent⁶.

The retention of restorations increases when there are more opposing surfaces, closer contact between parts and better performance of the cement regarding its mechanical properties and potential to achieve bonding (understanding bonding as micro-mechanical and/or chemical bonds between the liquid and the parts placed in contact)⁷. Proper selection and use of luting agent are extremely

important, as many of the advantages of this type of material will be lost if an inadequate bonding system is used⁸.

Resin cements on their own are not adhesive – they need to be supplemented with treatments of both the tooth surface and the restoration surface¹. Dental tissues need to be acid-conditioned before placing an adhesive system which will bond micro-mechanically to the tooth and chemically to the luting agent^{2,9}. This acid conditioning may be achieved independently with 37% phosphoric acid¹⁰ or by using sixth- or seventh-generation self-etch adhesive systems which contain acidic monomers. The non-dental surfaces also need to be conditioned for luting in order to create micro-retentions to favor micro-mechanical bonding to the luting agents^{2,8}.

Adhesive self-etch resin cements that do not require treatment of the tooth structure were introduced on the dental market a few years ago^{8,9,11}. They include monomers with phosphoric acid groups (phosphorylated methacrylates) that demineralize dental tissue and enable bonding, thereby simplifying the technique and saving time in the adhesive procedure^{2,12}.

Progress in the field of research, technological development and the advent of a wide range of self-etch adhesive cements motivated the current study, of which the aim is to ascertain whether self-etch adhesive cements provide one of the desirable properties for luting agents. Thus, the objective of the present work was to study *in vitro* the behavior of four self-etch adhesive cements regarding adhesion to the dentin structure and to compare them to a resin cement with classical bonding.

MATERIALS AND METHODS

This study evaluated the bond strength behavior of four self-etch resin cements compared to a conventional resin cement (described as conventional because it requires prior adhesive protocol including acid conditioning of tooth tissues before application). Seventy-five experimental specimens consisting of a ceramic test cylinder cemented to a dentin surface were prepared. Fifteen specimens were randomly assigned to each of the following groups: Group 1: RelyX U100 (3M Espe), Group 2: BisCem (Bisco), Group 3: MaxCem (Kerr), Group 4: seT PP (SDI), Group 5: RelyX ARC (3M Espe). The first four groups are self-etch resin cements, while Group 5 represents conventional cement and is the control group (Table 1).

Table 1: Experimental materials, manufacturer and batch.

Group	Experimental	Manufacturer Material	Batch
1	RELYX U100	3M ESPE. DENTAL PRODUCTS. USA	424360
2	BISCEM	BISCO INC. USA	1100002087
3	MAXCEM	KERR CORPORATION. USA	3498965
4	SET PP	SDI. AUSTRALIA	S0905891
5	RELYX ARC	3M ESPE DENTAL PRODUCTS. USA	N166655

The experimental specimens were prepared from 75 recently extracted non-carious human teeth (obtained from the Department of Surgery 2, School of Dentistry, Córdoba National University, with prior informed consent from patients). The teeth were stored in distilled water at 37 °C until they were processed experimentally.

The occlusal surfaces of third molars were cut horizontally with a low-speed saw (Isomet Low Speed Saw, Buehler, USA, Department of Dental Biology, School of Dentistry, Córdoba National University), with teeth mounted on an *ad hoc* positioning device (Fig.1). The cut surfaces were polished using rotating discs of decreasing grain size under constant water cooling (metallographic polisher; A.B.O.) until flat, polished surfaces were obtained approximately 2 mm beyond the dentin-enamel junction. Once the surfaces were polished,

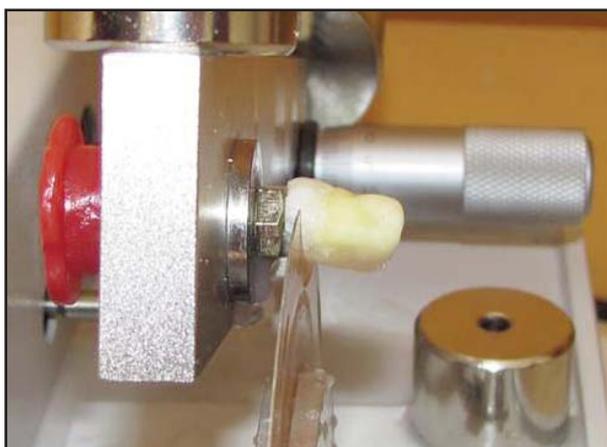


Fig. 1: Cross section of specimens.



Fig. 2: Specimens embedded in acrylic resin to be mounted on the universal testing machine.

the teeth were mounted in plastic shapers containing self-curing acrylic resin (Fig. 2) so that they could be attached to an *ad hoc* device for bond strength testing (Fig. 3).

The dentin surfaces in Groups 1 to 4, representing self-etch cements, received no prior treatment, but were simply washed with pressurized water and dried with cotton swabs, preserving dentin humidity. The dentin surfaces in Group 5 (control) were conditioned with 35% phosphoric acid gel (Scotch Bond Etchant, 3M Co.) for 15 seconds, washed with pressurized water for 15 seconds and dried for 5 seconds, after which the adhesive system (Single Bond 2, 3M Co) was applied, following the manufacturer's instructions.

Ceramic test cylinders (IPS Empress 2, Ivoclar-Vivadent) 4.1 millimeters in diameter were prepared (Eduardo Ruderman Dental Prosthetics Laboratory) (Fig. 4), to bond to the dentin surfaces using the different cements. The ceramic surfaces to be bonded were treated following manufacturer's instructions: etching with 10% hydrofluoric gel for 1 minute and silanization for 5 minutes, to complete evaporation (Monobond S, Vivadent.).



Fig. 3: Device for mounting on the universal testing machine.

Then the test cylinders were attached to the dentin surfaces using the different experimental self-etch resin cements (Groups 1 to 4) or the dual conventional cement (Group 5, control), strictly following the instructions of their respective manufacturers. The cement for each experimental group was placed on both the dentin surface and the ceramic surface. The dentin substrate was covered with an adhesive paper with a perforation of the same diameter as the ceramic test cylinders in order to limit the adhesion area (Fig. 5) and a constant 25N load was applied using a device for standardizing loads (Fig. 6). Any excess material was removed using a microbrush, and specimens were light-cured with a 540 mW/cm² halogen lamp (XL3000, 3M

ESPE. USA) for 30 seconds each on vestibular and lingual aspects.

Once the ceramic test cylinders were attached, each specimen was stored in distilled water and kept at a constant temperature of 37 °C until it was tested (Fig. 7). Specimens were tested mechanically under shear strain using a device specifically created for such purpose, mounted on a universal testing machine (Instron Corporation; Department of Dental Materials, School of Dentistry, Buenos Aires University), at 1mm/min crosshead speed.

In order to ascertain whether bond strength changed over time, the 15 specimens in each group were randomly assigned to subgroups of 5 specimens each to be tested at 7, 14 and 21 days.



Fig. 4: Ceramic test cylinders made from IPS Empress 2 (Ivoclar Vivadent). (Ruderman Dental Prosthetics Laboratory).



Fig. 5: Adhesive paper with a perforation of the same diameter as the ceramic test cylinders covering tooth surface to limit the adhesion area.



Fig. 6: Ad-hoc standardizing device for cementing force, applying a constant 25N load.



Fig. 7: Specimens immersed in distilled water until experimental processing.

Shear bond strength (MPa) was calculated from the relationship between shear load (N) and test cylinder surface area (mm). Data were recorded and analysis of variance and multiple comparison tests were performed to determine statistical significance.

RESULTS

Table 2 shows the mean values for bond strength in MegaPascals (MPa), standard deviation and confidence interval for each experimental material. RelyX ARC (control group) had the highest shear bond strength (15.52 MPa). The best behavior among self-adhesive cements was for RelyX U100 (10.08 MPa), with BisCem in second place (6.36 MPa) and MaxCem in third place (5.45 MPa), while SeT PP had the lowest bond strength (3.17 MPa).

Analysis of Variance (Table 3) showed no statistically significant difference ($p < 0.0001$) among the study materials. No difference in bond strength was found regarding time or material/time interaction.

Tukey's multiple comparisons test (Table 4) showed significant differences between materials, except for MaxCem and BisCem, which did not differ from each other, though they did differ from the rest.

The adhesive surfaces were analyzed after detachment of the ceramic test cylinders by observation under stereomicroscope at x20 magnification. Failure mode in bonding for all self-etch cements studied was adhesive, i.e., between cement and dentin.

Fig.8 shows the behavior of the different cements evaluated from the standpoint of bond strength at the three study times.

Table 2: Means, standard deviation and confidence interval (95%).

Group	Material	Means	S.D.	LL (95%)	LSD (95%)
1	RelyX U100	10.80	2.37	9.48	12.11
2	BisCem	6.36	1.70	5.42	7.30
3	MaxCem	5.45	1.36	4.69	6.20
4	seT PP	3.17	0.73	2.76	3.57
5	RelyX ARC	15.52	2.70	14.02	17.01

Table 3: Analysis of Variance.

Sources of variation	Sums of Squares	Degrees of Freedom	Mean Squares	F	p-value
Model	1479.51	14	105.68	28.35	<0.0001
Material	1448.27	4	362.07	97.12	<0.0001
time	7.21	2	3.60	0.97	0.3861
Material *time	24.03	8	3.00	0.81	0.6000
Error	223.67	60	3.73		
Total	1703.18	74			

Table 4: Multiple Comparisons Test.

Material	Means	n	S.E.
seT PP	3.17	15	0.50 A
MaxCem	5.45	15	0.50 B
BisCem	6.36	15	0.50 B
RelyX U100	10.80	15	0.50 C
RelyX ARC	15.52	15	0.50 D

Means with the same letter do not differ significantly ($p \leq 0.05$)
 Test: Tukey Alpha=0.05 LSD=1.98263
 Error: 3.7279 gl: 60

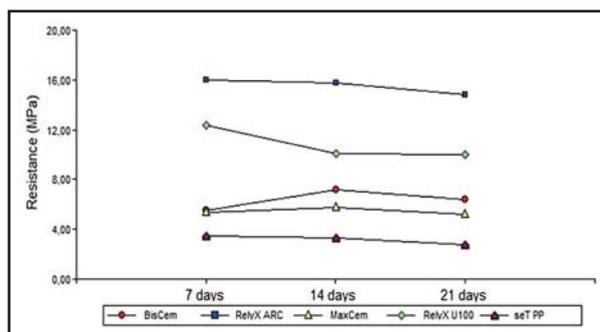


Fig. 8: Shear Bond Strength according to Material and Time.

DISCUSSION

The main advantage of self-adhesive cements is their quick and relatively simple application technique, which is one of the most desirable characteristics in dental materials because it reduces clinical steps, thereby saving operational time¹¹. Conventional resin cements requiring multiple steps for application involve a complex, sensitive technique which may affect the bonding efficacy between the restoration and the tooth¹³.

This study found significant differences in bond strength to dentin among the different experimental luting agents. Self-adhesive resin cements had significantly lower bond strength values than conventional, multi-step systems represented by the control group (RelyX ARC).

The low bond strength recorded for these cements is probably related to their low capacity for demineralizing and infiltrating the dentin substrate¹¹. Despite their low initial pH, their greater viscosity may explain why a true hybrid layer is not formed when they are applied to dentin¹⁴, since the quality of the dentin-cement interface is closely related to the extent of monomer infiltration into the demineralized dentinal collagen^{15,16}. This was confirmed in our study by observation under stereomicroscope, which showed that the bond failure mode was adhesive, i.e. between the cement and the dentin surface.

To promote efficient micro-mechanical bonding to dentin collagen fibers, these cements should be capable of conditioning the dental substrate in a relatively short time, which requires optimal wetting properties to ensure rapid interaction with dentin^{17,18}. As a general rule, polymer bonding depends on the surface energy and wetting capacity of the adhesive or luting agent to the substrate. Phosphoric acid etching produces an area with greater surface energy because it removes the smear layer and increases surface roughness, providing greater wettability^{19,20}. This may explain the higher bonding values of conventional resin cements, represented in this study by RelyX ARC (control group).

Some studies have reported better bonding values for self-conditioning cements with prior treatment of dentin with phosphoric acid. They suggest that the increase in dentin water content after acid etching²¹ may help create better ionization of acid monomers in the luting agents, enabling better

conditioning of the surface and better polymer bonding²²⁻²⁵. Nevertheless, other studies have reported lower bond strength values when acid etching is performed prior to applying self-etch cements²⁹. The difficulties in standardizing work methodologies, such as thickness of the smear layer, application of weight for cementing or preparation of test specimens make it impossible to compare the results reported by different authors.

The aim of this study was to evaluate four self-etch cements used according to their manufacturer's instructions, which is what dentists will ultimately do during their work. The results found in this and other studies suggest that dentists who choose these systems because they save time and require simple techniques should take into account their lower bond strengths to dental tissues, and avoid using them for preparations which have little or no retention. The lower bond strength may be partly or wholly attributed to the self-etch cements' ability to interact chemically with the hydroxyapatite in the dentin, rather than to micro-mechanical adhesion, since they only act superficially with dentin²⁶⁻²⁸.

Of the experimental materials evaluated, the lowest bond strength to dentin was found for MaxCem and seT PP. According to the manufacturers, the ability to self-etch is due to the presence of different acidic monomers in the formula of the cementing agents such as GPDM in MaxCem, and phosphorylated ester methacrylates in seT PP, whose acidic potential and concentration would be insufficient to promote dentin self-conditioning²⁹, in comparison to the phosphoric acid esters present in RelyX U 100, which presented higher bond strength. Another factor to consider is that once these cements polymerize, pH should change to a more neutral value. The study published in 2007 by Han¹⁷ showed that 48 hours after polymerization, only RelyX U100 presented a neutral pH value (7), whereas pH for MaxCem was 3.6. A low pH value lasting for some time may have deleterious impact on bonding strength to dentin^{17,30}.

Finally, the bond to ceramic was not analyzed in the current study, but it is worth noting that bonding effectiveness has been reported by several authors,^{5,9,31-36} who recommend treatment of ceramic surfaces by application of hydrofluoric acid and silane to ensure proper cement-ceramic adhesion, regardless of the cement used. In our experience, this is reflected by the fact that bond failures in all

cases were between resin cements and dentin, with no instance of cement-ceramic failure.

Based on the results of this study and within the limitations of an *in vitro* study, the following may be concluded:

The self-conditioning cements evaluated showed values for bonding to dentin which are significantly lower than those for the conventional resin cement which represented the control group.

The authors declare they have no conflict of interest with any of the companies manufacturing the cements used in this study.

ACKNOWLEDGMENTS

We thank Dr. Andrea Kaplan and staff at the Department of Dental Materials at the School of Dentistry, Buenos Aires University, for their support with the laboratory tests.

REFERENCES

- Bertacchini S, Cipponeri K. Medios cementantes adhesivos. *Rev Asoc Odontol Argent*; 2002; 90: 124-130.
- Hikita K, Van Meerbeek B, De Munck J, Ikeda T et al. Bonding effectiveness of adhesive luting agents to enamel and dentin. *Dent Mater* 2007; 23: 71-80.
- Bertoldi Hepburn A. Fijación de estructuras rígidas en odontología restauradora. En: *Rehabilitación Posendodóntica*. Cap. 9. 1° ed. Ed. Médica Panamericana, Buenos Aires, 2012; pp. 285-304.
- Barrancos Mooney J y col: Incrustaciones de porcelana. En: *Operatoria Dental. Integración clínica*. 5 ed. Ed. Médica Panamericana, Buenos Aires, 2015, pp. 1189-1204.
- Frankenberger R, Hartmann VE, Krech M, Krämer N, Reich S, Braun A, Roggendorf M. Adhesive luting of new CAD/CAM materials. *Int J Comput Dent* 2015; 18(1):9-20.
- Macchi RL y col. *Materiales Dentales*. Cap. 12. 4°ed. Bs. As, Argentina. Ed Panamericana, 2007, pp. 149-153.
- Bertoldi Hepburn A. Fijación de estructuras rígidas en odontología restauradora. Una revisión general. *Rev. Asoc. Odontol. Argent* 2007; 95: 403-416.
- Ferracane JL, Stansbury JW, Burke FJ. Self-adhesive resin cements - chemistry, properties and clinical considerations. *J Oral Rehabil* 2011; 38: 295-314.
- De Munck J, Vargas M, Van Landuyt K, Hikita K, Lambrechts P, Van Meerbeek B. Bonding of an auto-adhesive luting material to enamel and dentin. *Dent Mater* 2004; 20: 963-971.
- Buonocore MG. A simple method of increasing the adhesion of acrylic filling materials to enamel surfaces. *J Dent Res* 1955; 34: 849-853.
- Viotti RG, Kasaz A, Pena CE, Alexandre RS, Arrais CA, Reis AF. Microtensile Bond Strength of New Self Adhesive Luting Agents and Conventional Multistep Systems. *J Prosthet Dent* 2009; 102: 306-312.
- Goracci C, Cury A H, Cantoro A, Papacchini F, Tay F R, Ferrari M. Microtensile bond strength and interfacial properties of self-etching and self-adhesive resin cements used to lute composite onlays under different seating forces. *J Adhes Dent* 2006; 8: 327-335.
- Frankenberger R, Krämer N, Pestchelt A. Technique sensitivity of denting bonding: effect of application mistakes on bond strength and marginal adaptation. *Oper Dent* 2000; 25: 324-330.
- Monticelli F, Osorio R, Mazzitelli C, Ferrari M, Toledano M. Limited decalcification/diffusion of self-adhesive cements into dentin. *J Dent Res* 2008; 87: 974-979.
- Hashimoto M, Ito S, Tay FR, Svizero NR, Sano H, Kaga M, Pashley DH. Fluid movement across the resin-dentin interface during and after bonding. *J Dent Res* 2004; 83: 843-848.
- Zorzin J, Belli R, Wagner A, Petschelt A, Lohbauer U. Self-adhesive resin cements: adhesive performance to indirect restorative ceramics. *J Adhes Dent* 2014: 541-546
- Han L, Okamoto A, Fukushima M, Okiji T. Evaluation of physical properties and surface degradation of self-adhesive resin cements. *Dent Mater* 2007; 26: 906-914.
- Nawareg MM, Zidan AZ, Zhou J, Chiba A, Tagami J, Pashley DH. Adhesive sealing of dentin surfaces in vitro: A review. *Am J Dent* 2015; 28: 321-332.
- Van Meerbeek B, De Munck J, Yoshida Y, Inoue S et al. Buonocore memorial lecture. Adhesion to enamel and dentin: current status and future challenges. *Oper Dent* 2003; 28: 215-235.
- Toledano M. *Cementos dentales. Arte y Ciencia de los Materiales odontológicos* Madrid: Ediciones Avances 2003; pp. 253.
- Banomoyong D, Palamara JE, Burrow MF, Messer HH. Effect of dentin conditioning on dentin permeability and micro-shear bond strength. *Eur J Oral Sci* 2007; 115: 502-509.
- Erhardt MC, Cavalcante LM, Pimenta LA. Influence of phosphoric acid pretreatment on self-etching bond strengths. *J Esthet Restor Dent* 2004; 16: 33-40.
- Moszner N, Salz U, Zimmermann J. Chemical aspects of self-etching enamel-dentin adhesives: A systematic review. *Dent Mater* 2005; 21: 895-910.

24. Mazzitelli C, Monticelli F, Osorio R, Casucci A, Toledano M, Ferrari M. Effect of simulated pulpal pressure on self-adhesive cements bonding to dentin. *Dent Mater* 2008; 24: 1156-1163.
25. Baader K, Hiller KA, Buchalla W, Schmalz G, Federlin M. Self-adhesive Luting of Partial Ceramic Crowns: Selective Enamel Etching Leads to Higher Survival After 6.5 Years In Vivo. *J Adhes Dent* 2016; 18: 169-179.
26. Yoshida Y, Nagakane K, Fukuda R, Nakayama Y et al. Comparative study on adhesive performance of functional monomers. *J Dent Res* 2004; 83: 454-458.
27. Gerth HU, Dammaschke T, Zuchner H, Schafer E. Chemical analysis and bonding reaction of RelyX Unicem and Bifix composites - a comparative study. *Dent Mater* 2006; 22: 934-941.
28. Dos Santos VH, Griza S, de Moraes RR, Faria-E-Silva AL. Bond strength of self-adhesive resin cements to composite submitted to different surface pretreatments. *Restor Dent Endod* 2014; 39: 12-6.
29. Turp V, Sen D, Tuncelli B, Özcan M. Adhesion of 10-MDP containing resin cements to dentin with and without the etch-and-rinse technique. *J Adv Prosthodont* 2013; 5: 226-233.
30. Costa LA, Carneiro KK, Tanaka A, Lima DM, Bauer J. Evaluation of pH, ultimate tensile strength, and micro-shear bond strength of two self-adhesive resin cements. *Braz Oral Res* 2014; 28: 1-7.
31. Hölland W, Schweiger M, Frank M, Rheinberger V. A comparison of the microstructure and properties of the IPS Empress 2 and the IPS Empress glass-ceramic. *J Biomed Mater Res* 2000; 53: 297-303.
32. Borges GA, Sophr AM, de Goes MF, Sobrinho LC, Chan DC. Effect of etching and airborne particle on the microstructure of different dental ceramics. *J Prosthet Dent* 2003; 89: 479-488.
33. Della Bona A, Anusavice KJ, Mecholsky JJ Jr. Failure analysis of resin composite bonded to ceramic. *Dent Mater* 2003; 19: 693-699.
34. Piwowarczyk A, Bender R, Ottl P, Lauer HC. Long-term bond between dualpolymerizing cementing agents and human hard dental tissue. *Dent Mater* 2007; 23:211-217.
35. Peumans M, Voet M, De Munck J, Van Landuyt K, Van Ende A, Van Meerbeek B. Four-year clinical evaluation of a self-adhesive luting agent for ceramic inlays. *Clin Oral Investig*. 2013; 17:739-750.
36. Uludag B, Yucedag E, Sahin V. Microleakage of inlay ceramic systems luted with self-adhesive resin cements. *J Adhes Dent* 2014; 16: 523-529.